

Evaluating the Deterioration of Galvanized Steel in an Acidic Medium using *Pinus Oocarpa* Seed Extract as Inhibitor

M. O. Nkiko*

Department of Physical and Chemical Sciences, Faculty of Basic and Applied Science, Elizade University, Ilara-Mokin, P.O. Box. 002, Ilara-Mokin, Ondo State, Nigeria

*Corresponding author: mojisola.nkiko@elizadeuniversity.edu.ng

Received 08/07/2019; accepted 20/06/2021

<https://doi.org/10.4152/pea.2022400202>

Abstract

Pinus oocarpa seed extract corrosion inhibition effect on galvanized steel has been studied in 2 M hydrochloric acid, at 303 K and 333 K, by gravimetric methods. The inhibitor efficiency decreased with higher temperatures, which suggests physisorption. Potassium iodide (KI) synergistic action produced an increase in the extract inhibition efficiency, but its parameter decreased with higher inhibitor concentrations. The galvanized steel optical microscopy shows that the metal surface was coated with *P. oocarpa* seed extract, and that the cracks observed in the inhibitor absence were filled. This observation suggests that the extract can be used as a coating to prevent galvanized steel corrosion.

Keywords: corrosion inhibitor, optical microscopy, gravimetric methods, *P. oocarpa* and synergistic effect.

Introduction

Steel of different grades is extensively used in different domestic and industrial applications. It has equally been observed that industrial acid pickling and oil-well acidizing cause rapid corrosion of steel structures (1, 2). The industry is replete with various technological attempts at proffering solutions for preventing corrosion through material selection, novel design strategies and the deployment of diverse protective techniques. The application of inhibitors as a reliable approach to the metallic materials protection from corrosion is well documented. (1-24). The use of eco-friendly and biodegradable green inhibitors, obtained from cheap and readily available naturally occurring extracts of plant and animal origin, has generated much interest in recent times. Extracts from several plants have been reported to inhibit the metals corrosion in acidic media (2, 12-24).

The present study investigated the *Pinus oocarpa* seed extract inhibitive effects on galvanized steel corrosion in hydrochloric acid (HCl), using the gravimetric method. The potassium iodide (KI) synergistic effect on the extract inhibition efficiency was also analysed. The obtained result is aimed at developing an efficient, biodegradable and environmentally friendly protection that will prevent material loss and reduce corrosion control economical costs. *P. oocarpa* is non-toxic and biodegradable. It is also readily available in the Nigerian flora.

P. oocarpa is of the family *pinaceae*, it is as an egg-cone pine and an evergreen tree. It has been reported as a medicinal plant (25) and it is an important commercial plant for wood production in the paper industry (26). Rubio, et al. (27) found that the *P. oocarpa* major constituent – oleoresin – contains two effective diterpenes on trypanosomacruzi epimastigotes. Philipson and Wright (28) have shown that terpenes extracted from this plant are active against parasitic protozoans.

Materials and methods

Galvanized steel coupons, with the dimensions of 4.5 cm by 3 cm, were polished using various emery paper grades. The polished coupons were washed with distilled water, degreased with absolute ethanol followed by acetone, dried and stored in an air-tight desiccator, to avoid moisture prior to use (10, 14).

P. oocarpa seeds were collected from the flora of the Olabisi Onabanjo University Mini-Campus, Ago- Iwoye, and classified at the Federal Research Institute of Nigeria (FRIN), FHI number 108780. The seeds were dried and ground to powder. Continuous solvent extraction was carried out with methanol. The excess solvent was distilled, and the extract was left overnight to crystallize. The crystals obtained from the powdered seed extract were stored in an air-tight desiccator and used without further purification. Inhibitor test solutions were prepared at the concentrations from 1 g to 5 g (W/V), with an appropriate quantity of 2 M HCl, in a total volume of 100 mL.

Previously prepared galvanized steel was weighed and immersed in 100 mL of different test solution concentrations. The coupons were retrieved every 2 h, washed and reweighed. The differences in the coupons weight were taken as the weight loss evaluated in grams. Corrosion investigations were undertaken at the temperatures of 303 K and 333 K, and in 2 M HCL.

The *P. oocarpa* inhibition efficiency was calculated using the equation:

$$I \% = (w_o - w_i)w_o^{-1} \times 100 \quad (1)$$

The degree of surface coverage (θ) was calculated from the equation:

$$\theta = (w_o - w_i)w_o^{-1} \quad (2)$$

and corrosion rate (mm/yr.) was evaluated using the formula:

$$CR = 87.6W/\rho At \quad (3)$$

where, for galvanized steel, W is the weight loss (g), ρ is the density given as $7.85 \times 10\text{gcm}^{-3}$, A is the cross -sectional area (cm^2) and t is exposure time in h. The halide additive synergistic effect was studied by adding 10.0 mM KI to 3 g of the *P. oocarpa* extract test solution.

Results and discussion

P. oocarpa extract inhibition efficiency on galvanized steel corrosion and weight loss

Galvanized steel weight loss decreased with time and *P. oocarpa* seed extracts higher concentrations (Fig. 1). The inhibitor efficiency decreased with time and increased with its higher concentrations (Fig 2). However, its inhibition

efficiency decreased with a rise in temperature (Fig. 3). These observations presuppose that the inhibitor has covered a larger metal surface area, when its concentration was increased. The decrease in *P. oocarpa* inhibition efficiency with higher temperatures depicts the inhibitor physical adsorption mechanism onto the metal surface. Fig. 4 shows the corrosion rate temperature dependence on the inhibitor concentration.

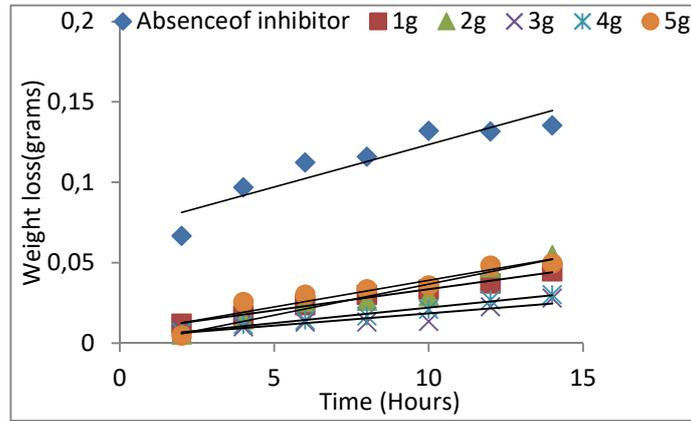


Figure 1. Galvanized steel weight loss dependence on time, in 2 M HCl with and without *P. oocarpa*.

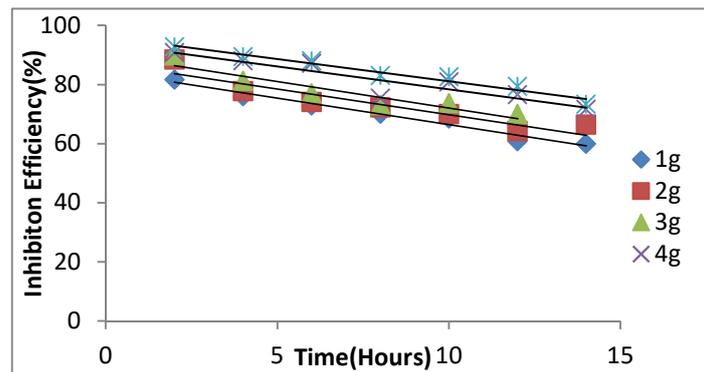


Figure 2. *P. oocarpa* inhibition efficiency dependence on time, at 30 °C.

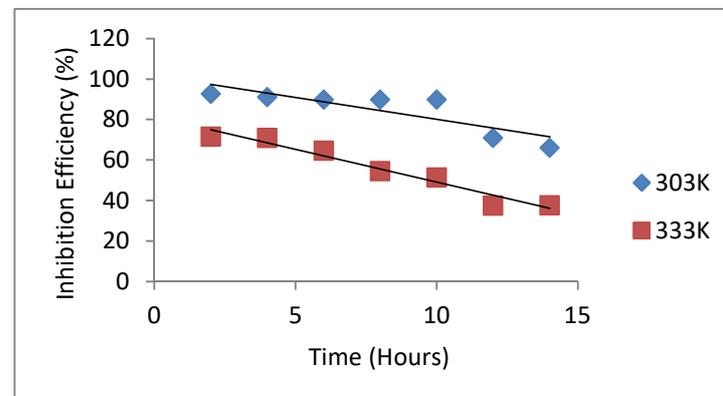


Figure 3. *P. oocarpa* inhibition efficiency dependence on temperature. The corrosion rate increases with a rise in temperature and decreases with higher inhibitor concentrations (Fig. 4).

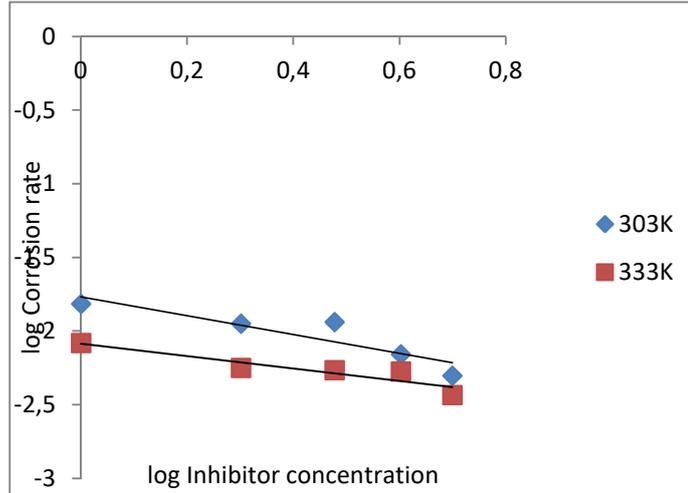


Figure 4. Corrosion rate temperature dependence with higher inhibitor concentrations.

Thermodynamic parameters of galvanized steel corrosion in 2 M HCl

The *P. oocarpa* surface coverage values best fitted to Langmuir model (Fig. 5) represented by the equation (4):

$$\frac{c}{\theta} = \frac{1}{K_{ads}} + C \quad (4)$$

The *P. oocarpa* seed extract composition is complex. Therefore, its components may be attractive or repulsive towards the galvanized steel surface, and its adsorption may occur at the anodic or cathodic sites of the latter. Thus, the adsorption onto the galvanized steel surface is represented by the modified Langmuir isotherm shown as equation (5):

$$\frac{c}{\theta} = \frac{1}{k_{ads}} + nC \quad (5)$$

where C is the inhibitor concentration, θ is its surface coverage area and n is a measure of its inhibition efficiency.

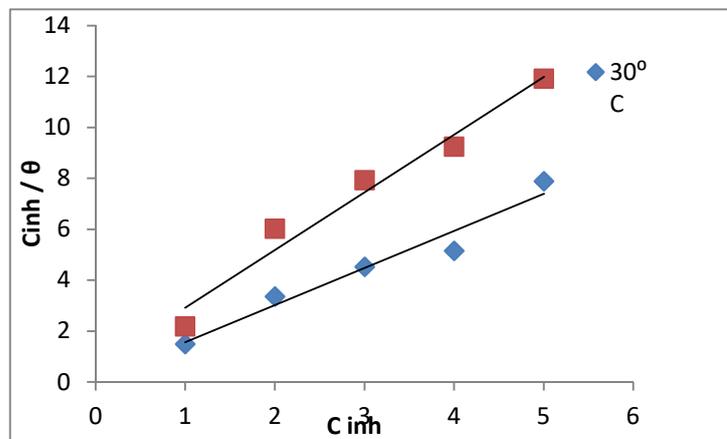


Figure 5. Langmuir's adsorption isotherm for galvanized steel corrosion inhibition by *P. oocarpa*.

Table 1 shows the thermodynamic parameter obtained from the Langmuir's adsorption isotherm. The obtained free energy of adsorption is negative, and lower than -20 kJ/mol. The equilibrium constant of adsorption, K_{ads} , decreases at higher temperatures. The inhibitor efficiency (N) was enhanced as the temperature was increased from 303 K to 333 K. These observations suggest that *P. oocarpa* was physically adsorbed by the metal. The enthalpy of adsorption, ΔH_{ads} , reported for this study was obtained from the Van't Hoff's equation, it is negative, and its magnitude increases at higher temperatures. So, this observation implies that the inhibition efficiency decreases as the temperature increases.

Table 1. Thermodynamic parameters for steel corrosion inhibition by *P. oocarpa*.

Temperature (K)	K_{ads}	N	ΔG_{ads} (kJ)	ΔH_{ads} (kJ)	ΔS_{ads} (J)
303	9.141	1.460	-15.692	- 5.574	70.185
333	1.513	1.617	-12.266	- 1.147	40.279

Iodide ions synergistic effect on P. oocarpa extract inhibitive properties

The synergistic parameter obtained in Table 2 has been calculated from the Aramaki and Hackerman equation (29).

$$S_i = (1 - I_{1+2})(1 - I'_{1+2})^{-1} \quad (6)$$

where $I_{1+2} = I_1$ is the halide ion inhibition efficiency, I_1 is the *P. oocarpa* extract inhibition efficiency and I' is the halide and *P. oocarpa* extract measured inhibition efficiency.

Table 2. KI synergistic effect on galvanized steel corrosion in 2 M HCL with *P. oocarpa* extract.

Inhibitor concentration (g)	Synergistic parameter S_i
1	1.951
2	1.938
3	1.764
4	1.874
5	1.787

The synergistic parameter values obtained in this study are greater than 1, which suggests a synergism between iodide ions and the *P. oocarpa* seed extract. It has been reported that the iodide ions strong adsorption and the electrostatic interactions of the inhibitor cations with the metal surface enhance inhibition efficiency (19, 30-31). Thus, the chemically adsorbed *P. oocarpa* iodide ions effect, on galvanized steel, increased the inhibitor adsorption surface area and, thereby, enhanced the extract inhibition efficiency.

Fig. 6 shows that the iodide ions synergistic effect is more pronounced at 60 °C, when compared to that at the lower temperature of 30 °C.

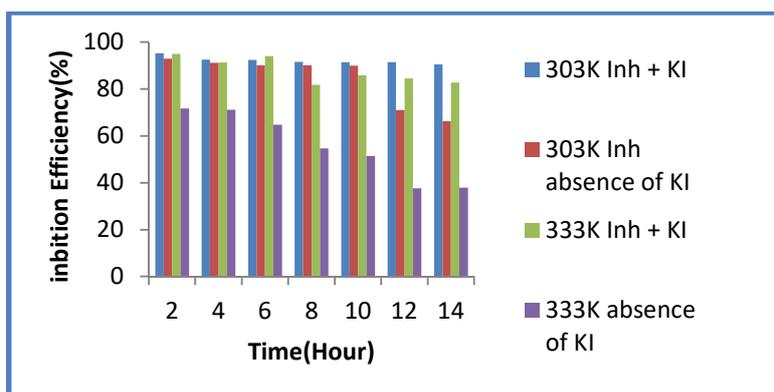


Figure 6. Temperature dependence of the 10 mM KI synergistic effect on *P. oocarpa* inhibition efficiency.

Galvanized steel optical microscopy with P. oocarpa extract

Fig. 7(A–C) shows the optical micrographs obtained for this study using the Foundrax Brinell Microscope type 2BM15, serial number 100332. Fig. 7A and 7B shows galvanized steel before and after immersion in a corrosive environment (2 M HCl), respectively. The metal surface in Fig. 7A is smooth, with minimum cracks that are greater in Fig. 7B. The cracks observed in Fig. 7B may result from the combination of applied stress and the acidic solution (32). Fig. 7C is the micrograph of galvanized steel immersed in 2 M HCl with *P. oocarpa*. Fig. 7D is the micrograph of galvanized steel to which the inhibitor and 10 mM KI were added. The cracks observed in Fig. 7B appeared to have been significantly filled, and in Fig. 7C are even less pronounced, due to the synergism between KI and the inhibitor, as shown in Fig. 7D. This implies that *P. oocarpa* is an effective inhibitor and can be used as a surface coating for galvanized steel.

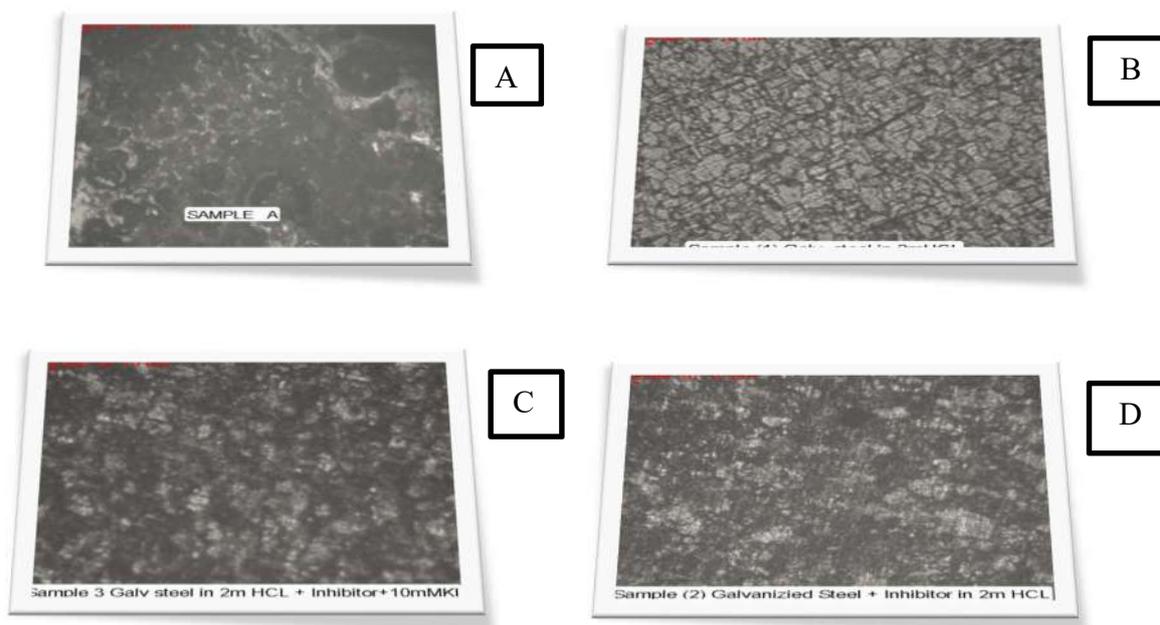


Figure 7. Optical micrograph of galvanized steel: (A) before immersion in a 2 M HCl blank solution; (B) after immersion in 2 M HCl; (C) in 2 M HCl added with *P. oocarpa*; and (D) in 2M HCl added with inhibitor and 10 mM KI.

Conclusion

P. oocarpa seed extract acts as an efficient inhibitor of galvanized steel corrosion. The extract inhibition efficiency increased with its higher concentration and decreased with the longer immersion time of the metal. However, the inhibitor efficiency decreased at higher temperatures, which presupposes a physical adsorption mechanism. *P. oocarpa* inhibitive effect was enhanced by the potassium iodide addition to the test solution. The inhibitor reduced the inter-granular stress cracks in the galvanized steel used for this study.

Acknowledgement

The author is grateful to the Midland Galvanizing Company, Abeokuta, especially, to Mr Adams, for having supplied galvanized steel for this study, and to Mr Habib, of Nigeria Foundry Limited, for having carried out the optical microscopy studies using the Foundrax Brinell Microscope type 2BM15, serial number 100332.

Author tasks

Conceived and designed the analysis; collected the data; provided for data or analysis tools; performed the analysis; wrote the paper.

References

1. Ramesh S, Rajeswari S, Maruthamuthu S. Effect of Inhibitors and Biocide on Corrosion of mild steel in natural aqueous environment. Mater Lett. 2003;57:4547-4554. Doi: [https://doi.org/10.1016/S0167-577X\(03\)00360-4](https://doi.org/10.1016/S0167-577X(03)00360-4)
2. Bammou L, Salghi R, Zarrouk A, et.al. Inhibition Effect of Natural Junipers Extract towards Steel Corrosion in HCL Solution. Int J. Electrochem Sci. 2012;7:8974-8987.
3. Ravari FB. Investigation on two saline type Schiff base compounds as corrosion inhibition of copper in 0.5 MH₂SO₄. J Sci. 2009;22(3):175-182.
4. Breakell JE, Siegwart M, Foster K, et al. Management of Accelerated Low Water Corrosion in Steel Maritime Structures 634 - CIRIA Series. 2005.
5. Finšgarand M, Milošev I. Inhibition of copper corrosion by 1, 2, 3-benzotriazole: A review. Corros Sci. 2010;52:2737-2749. Doi: <https://doi.org/10.1016/j.corsci.2010.05.002>
6. Singh AK, Qurashi MA. Piroxican: A novel corrosion inhibitor for mild steel corrosion in HCL solution. J Mater Environ Sci. 2010;1(2):101-110.
7. Niamien PM, Kouassi H.A, Trokourrey A, et.al. Copper Corrosion Inhibition in 1 M HCL by two Benzimidazole Derivatives. ISRN. Mater Sci. 2012;2012:1-15. Doi: <https://doi.org/10.5402/2012/623754>
8. Villami RF, Curio VP, Rubinand JC, et al. Effect of sodium dodecyl sulfate on copper corrosion in sulphuric acid media in the presence and absence of benzotriazole. J Electroanal Chem. 1999;472(2):112-119.

9. Mobin M, Parveen M, Rafiquee MZA. Synergistic effect of Sodium dodecyl sulphate and Cetyltrimethyl ammonium bromide on the corrosion inhibition behavior of L- Methionine on mild steel in acidic medium. Arabian J Chem. 2013. Doi: <https://dx.doi.org/10.1016/j.arabjc.2013.04.006>
10. Hernandez-Alvarado LA, Hernandez LS, Rodriguez-Reyna SI. Evaluation of Corrosion Behaviour of Galvanized Steel treated with Conventional Coatings and a Chromate-Free Organic Inhibitor. Int J Corros. 2012;2012:1-9. Doi: <https://doi.org/10.1155/2012%2F368130>
11. Khan MU, Ahmad S, Al-Gahtan HJ. Chloride-Induced Corrosion of Steel in Concrete: An Overview on Chloride Diffusion and Prediction of Corrosion Initiation Time Chloride-Induced Corrosion of Steel in Concrete: An Overview on Chloride Diffusion and Prediction of Corrosion Initiation Time. Int J Corros. 2017;2017:1-9. Doi: <https://doi.org/10.1155/2017/5819202>
12. Hou Y, Lei D, Li S, et al. Experimental Investigation on Corrosion Effect on Mechanical Properties of Buried Metal Pipes. Int J Corros. 2016;2016:1-13. Doi: <https://doi.org/10.1155/2016/5808372>
13. Qiang Y, Guo L, Zhang S, et al. Synergistic effect of tartaric acid with 2,6-diaminopyridine on the corrosion inhibition of mild steel in 0.5 M HCL. Scientif Rep. 2016;6:1-14. Doi: <https://doi.org/10.1038/srep33305>
14. Nkiko MO, Bamgbose JT. Corrosion Inhibitive Effect of *Ocimum Gratissimum* Extract on Zinc-Aluminium Alloy in Hydrochloric Acid. Port Electrochim Acta. 2011;29(6):419-427. Doi: <https://doi.org/10.4152/pea.201106419>
15. Afia L, Salghi R, Bazzi El, et al. Testing Natural Compounds; *Argania Spinose* Kernels Extract and Cosmetic Oil as Eco-friendly Inhibitors for Steel in 1 M HCL. Int J Electrochem Sci. 2011;6: 5918-5939.
16. Znini M, Majidi L, Laghchimi A, et al. Chemical Composition and Anticorrosive Activity of *Warionia Saharea* Essential Oil against the Corrosion of Mild Steel in 0.5 M H₂SO₄. Int J Electrochem Sci. 2011;6:5940-5955.
17. Nkiko MO, Oguntoyinbo ES, Bamgbose JT, et al. Protection of Zinc Alloy In H₃PO₄ Using Extract of *Lantana Camara*. Life Sci J. 2014;11(11):899-904. Doi: <https://dx.doi.org/10.7537/marslsj111114.160>
18. Ebenso EE, Eddy NO, Odiongenyi AO. Corrosion Inhibitive properties and adsorption behaviour of ethanol extract of *Piper guinensis* as green corrosion inhibitor for mild steel in H₂SO₄. Afri J Pure and Appl Chem. 2008;29(11): 107-115.
19. Obot IB, Obi-Egbedi NO, Umoren SA, et al. Synergistic and Antagonistic Effects of Anions and *Ipomoea Invulcrata* as Green Corrosion Inhibitor for

- Aluminium Dissolution in Acidic Medium. Int J Electrochem Sci. 2010;5(7):994-1007.
20. Okafor PC, Ikpi ME, Uwah IE, et al. Inhibitory action of *Phyllanthus amarus* extracts on the corrosion of mild steel in acidic media. Corros Sci. 2008;50(8):2310-2317. Doi: <http://dx.doi.org/10.1016/j.corsci.2008.05.009>
 21. Akalezi CO, Oguzie EE. Evaluation of anticorrosion properties of *Chrysophyllum albidum* leaves extract for mild steel protection in acidic medium. Int J Ind Chem. 2015;1-12. Doi: <https://doi.org/10.1007/s40090-015-0057-5>
 22. Njoku DI, Onuoha GN, Oguzie EE, et.al. *Nicotiana tabacum* leaf extract protects aluminium alloy AA3003 from acid attack. Arabian J Chem. 2016; 2016:1-13. Doi: <http://dx.doi.org/10.1016/j.arabjc.2016.07.017>
 23. Muthukrishnan P, Jeyaprabha B, Prakash P. Mild steel corrosion inhibition by aqueous extract of *Hyptis suaveolens* leaves. Int J Ind Chem. 2014;5(5):1-11. Doi: <https://doi.org/10.1007/s40090-014-0005-9>
 24. Alaneme KK, Olusegun SJ. Corrosion inhibition performance of Lignin of Sunflower (*Tithonia diversifolia*) on Medium Carbon Low Alloy Steel Immersed in H₂SO₄ Solution. Leonardo J Sci. 2012;20:59-70.
 25. Aguilar A, Camacho JR, Chinos S, et.al. Herbario Medicinal del Instituto Mexicano de Seguro Social – Information etnobotannica. Institution Mexicano del Seguro Social. Mexico, D.F. 1994;180.
 26. Drovak WS, Hodge GR, Gutierrez EA, et al. Conservation and Testing of Tropical and Subtropical Forest Species by the Camcore Cooperative College of Natural Resources, NCSU. Raleigh, NC.USA, 2000.
 27. Rubio J, Calderon JS, Flores A, et al. Trypanocidal activity of Oleresin and Terpenoids isolated from *Pinus oocarpa*. Zetschrift fier Naturforsch C J Biosci. 2005;60(9-10):711-716. Doi:<https://doi.org/10.1515/znc-2005-9-1009>
 28. Philipson JD, Wright CW. Antiprotozoalagents from plant sources. Planta Med. 1991;57:53-59. Doi: <https://doi.org/10.1055/s-2006-960230>
 29. Aramaki K, Hackerman N. Inhibition Mechanism of Medium-sized Polyemethyleneimine. J Electrochem Soc. 1969;116(5):568-574. Doi: <https://doi.org/10.1149/1.2411965>
 30. Amin MA, Moshen Q, Hazzazi OA. Synergistic effect of I⁻ ions on the corrosion of Al in 1.0 M phosphoric acid solution. Mater Chem Phys. 2009;114:908-914. Doi: <https://doi.org/10.1016/j.matchemphys.2008.10.057>
 31. Founda AS, Al-Sarawy AA, El-Kateri EE. Pyrazolone derivatives as corrosion inhibitors of C – steel in hydrochloric acid solution. Desalination. 2006;201:1-13. Doi: <https://doi.org/10.1016/j.desal.2006.03.519>
 32. Callister WD (Jr). Material Science and Engineering - An Introduction, 4th Ed, NY, Wiley, 1997.